

AD-A041 176

NEW ORLEANS UNIV LA DEPT OF CHEMISTRY

F/G 8/1

INFRARED AND NUCLEAR MAGNETIC RESONANCE ANALYSIS OF ORGANOTIN T--ETC(U)

JUN 77 J E HOFFMAN, K C KAPPEL, L M FRENZEL

N00014-76-C-0836

UNCLASSIFIED

TR-1

NL

4 OF 12
AD
A041176



END

DATE
FILMED
7-77

ADA 041176

Office of Naval Research

Contract No. N00014-76-C-0836

Project No. NR 356-626

Technical Report No. 1

INFRARED AND NUCLEAR MAGNETIC RESONANCE
ANALYSIS OF ORGANOTIN TOXICANTS FOR
MARINE ANTIFOULING COATINGS

by

James E. Hoffman, Keith C. Kappel, Lydia M. Frenzel
and Mary L. Good

Prepared for publication in Organometallic
Polymers, C. E. Carraher, Jr. and C. Pittman,
Jr., Editors. (Proceedings at a Symposium
sponsored by the ACS Division of Organic
Coatings and Plastics at the New Orleans
National ACS Meeting, March, 1977.)

to be published by Academic Press, 1977

Department of Chemistry

University of New Orleans

Lakefront, New Orleans, La. 70122

June 24, 1977

Reproduction in whole or in part is permitted for
any purpose of the United States Government

Approved for Public Release; Distribution Unlimited

AD No.
DDC FILE COPY

DDC

JUL 5 1977

D

INFRARED AND NUCLEAR MAGNETIC RESONANCE
ANALYSIS OF ORGANOTIN TOXICANTS FOR
MARINE ANTIFOULING COATINGS

James F. Hoffman, Keith C. Kappel,
Lydia M. Frenzel and Mary L. Good
University of New Orleans

ACCESSION for	
DTM	White Section <input checked="" type="checkbox"/>
DDC	Buff Section <input type="checkbox"/>
UNANNOUNCED <input type="checkbox"/>	
JUSTIFICATION	
BY	
DISTRIBUTION/AVAILABILITY CODES	
SPECIAL	

A

Infrared and nuclear magnetic resonance spectroscopies have been employed to elucidate the chemical and structural properties of triorganotin compounds incorporated into marine antifoulant coating formulations. It is necessary to determine the molecular species of the toxicant in order to be able to predict the mechanism of toxicant release and to design new, more effective coatings. In two conventional vinyl antifoulant coatings, the toxicant was found to react with one component in the coating formulation to yield different triorganotin compounds. A change in the $\nu_{\text{asym}}(\text{SnC})$ vibration was found to correlate with a change in the coordination geometry of tin. These results indicate that infrared spectroscopy is a powerful technique that can provide insights into the chemical processes occurring in the antifouling coatings.

I. INTRODUCTION

The problem of marine "fouling" of ship hulls and marine installations is well known and has been attacked by many research and development groups. Even the popular press and general technology periodicals have recently highlighted the problem in their publications (1,2,3). The present national difficulties associated with energy shortages make this fouling problem even more crucial. For example, "the drag caused by only a six-month accumulation of marine foulants can force a vessel to burn 40 percent more fuel just to maintain normal cruising speed" (1). Thus any attempt at fuel economy in the shipping industry and in the Navy must place the development of effective antifoulant procedures as a high priority item. The only practical solution through the years has been the utilization of paints and coatings having antifoulant activity. Most of the coatings which have been

DDC
RECEIVED
JUL 5 1977
RECEIVED
D

developed are paint formulations containing a toxicant component. The most widely used toxicant has been cuprous oxide although various compounds of arsenic, mercury, lead and tin have been used. The cuprous oxide coatings are good fouling inhibitors but they have rather short effective life-times. The arsenic, mercury and lead coatings have severe toxicological problems and have been either restricted in use or completely removed from the commercial market. The tin containing coatings have been investigated by a number of groups, particularly by researchers at the Naval Ship Research and Development Center at Annapolis, Maryland. Studies have shown that tin antifoulants possess several advantages over conventional copper antifoulants (4,5). For example, they provide superior antifouling over a longer period of time. When applied on conductive substrates, they do not promote corrosion as do copper based coatings. They exhibit control over several types of algae and barnacles when properly formulated. It has been proposed that the organotin compounds degrade to non-toxic, non-cummulative inorganic forms of tin, but there is no experimental evidence to support this proposition (6,7,8). Thus, the most promising antifoulant coatings which have been designed and characterized are those containing organotin toxicants.

Although the formulation of new coatings containing organotin moieties has been an area of active research, the determination of the chemical form of the toxicant in the bulk and on the surface of the coatings, and the elucidation of the surface release mechanism have received less attention. Thus, this initial report on our studies of these coating systems will review our efforts to devise procedures and background data which will allow the nature of the organotin toxicants to be determined by infrared and proton NMR spectroscopies. It is anticipated that these studies and other related work will eventually provide the tools for the identification of the chemical composition of the tin toxicants as a function of the coating matrix, the curing process, actual aging in normal use, and coating efficiency. Information of this type is essential for the design of new, more effective coatings and for the evaluation of the long term environmental impact of the widespread use of these toxic material.

The most effective and widely used organotin coating additives are the triorganotin compounds (R_3SnX where R = alkyl or phenyl and X = F, Cl, Br, I, OH, OCOR, $OSnR_3$, SnR_3 or acrylate). The tributyltin compounds have been used most extensively to date. These materials exhibit a much higher level of toxicity to marine foulants than they do to mammals. The shorter chained alkyls exhibit a high toxicity to mammals and a low toxicity to marine life (9). Thus this initial study is devoted to the evaluation of coatings containing trialkyltin species with special emphasis on the


tributyl series. Two general classes of coatings are being investigated: (1) conventional formulations consisting of an organotin compound, usually either bis(tri-n-butyltin) oxide (TBTO) or tri-n-butyltin fluoride (TBTF), thoroughly mixed with the rest of the coating components; and (2) newly developed coating systems consisting of R_3SnX moieties (where X is vinyl, acrylate, or maleate) polymerized or copolymerized through the unsaturated X groups. The conventional coatings presumably have free toxicant not bound to the coating matrix while in the polymer materials the toxicant species is covalently bonded to the matrix. Neat organotin materials have been examined to provide baseline spectra and spectral assignments of functional groups. Correlation techniques have been used to assign the SnC_3 , $Sn-X$, $Sn-O$ and COO vibrational modes in the infrared spectra. These assignments have then been used for the identification of functional groups and chemical entities in the coating formulations.

II. EXPERIMENTAL


Transmission infrared spectra for liquid samples were obtained as thin films between KBr and polyethylene disks in the region $4000-200\text{ cm}^{-1}$. The spectra of solid samples were obtained as KBr pellets. The spectra were recorded on a Perkin-Elmer Infrared Spectrophotometer Model 283 equipped with a printer accessory, which provides a digital readout of peak positions and relative intensities of the peaks. Peak positions are accurate to $\pm 3\text{ cm}^{-1}$ in the region $4000-2000\text{ cm}^{-1}$, and to $\pm 1.5\text{ cm}^{-1}$ in the region $2000-200\text{ cm}^{-1}$. Proton nuclear magnetic resonance (1H nmr) spectra were recorded on a Hitachi Perkin-Elmer R-20B spectrometer operating at a frequency of 60.0 MHz. The organotin and polymer samples were dissolved in $CHCl_3$, $CDCl_3$, and CCl_4 to give a 10% (w/v) solution with a few drops of tetramethylsilane (TMS) added as an internal reference.

Organotin compounds were obtained from M&T Chemicals, Inc. and were used without further purification. Purity was checked by chemical analysis and by 1H nmr. The conventional coatings, which contained $(Bu_3Sn)_2O$ and Bu_3SnF were donated by Glidden-Durkee, Standard Paint and Varnish Company of New Orleans, and by the U. S. Navy. All coatings investigated were vinyl based formulations. The Glidden-Durkee coating contains $(Bu_3Sn)_2O$ as the toxicant. The coating from the Standard Paint and Varnish Company (Alum-A-Tox) contains Bu_3SnF . The Navy formulation, 1020A, contains both $(Bu_3Sn)_2O$ and Bu_3SnF as toxicants. Formulations were also obtained which did not contain the toxicants. Experimental organotin containing polymers (CMP's) were donated by Dr. E. Fischer of the David Taylor Naval Ship Research and Development Center (DTNSRDC). The compositions of these polymers are as follows:

OMP-1 is poly (tri-n-butyltin methacrylate/tri-n-propyltin methacrylate/methyl methacrylate); OMP-2 is poly (tri-n-butyltin methacrylate/methyl methacrylate); OMP-4 is the tri-n-butyltin ester of poly (methylvinylether/maleic acid). The formulas for these materials are shown diagrammatically below.

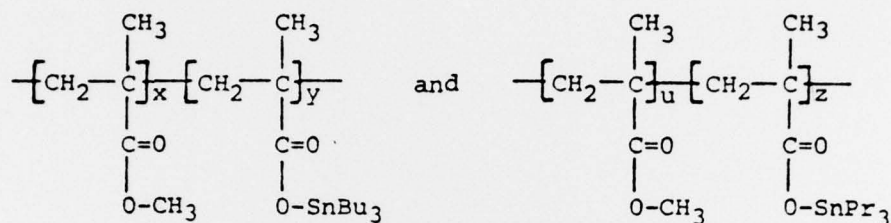

OMP 1

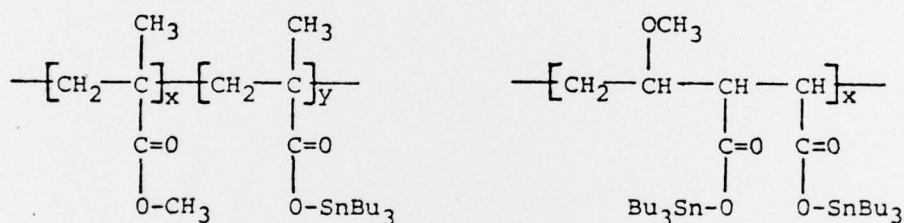

OMP 2

OMP 4

III. RESULTS AND DISCUSSION

Assignments of the infrared vibrations of the triorganotin compounds were made by the correlation method, since these are complex molecules and few spectral assignments of comparable compounds are available in the literature (10,11). The Sn-X, Sn-O, and SnC₃ vibrations are of particular interest because these functional groups are the most likely ones to be affected by the leaching of the toxicant from the coating matrix. All of these vibrations occur below 1100 cm⁻¹. Other vibrations of importance to this study are ν_{OH}, which occurs around 3600 cm⁻¹, and the asymmetric and symmetric stretching frequencies, ν_{asym}(COO) and ν_{sym}(COO), of the carboxylate group. These vibrations are located between 1650 and 1300 cm⁻¹. Assignments of the vibrational modes of interest are presented in Table I.

Triorganotin compounds (R₃SnX) exhibit either a tetrahedral or a trigonal bipyramidal geometry depending on the nature of the X group. When X is capable of acting as a bridging ligand (e.g. F, OH, OCOCH₃), the organotin compound exhibits a trigonal bipyramidal geometry with the X group bridged between planar SnR₃ moieties. With other X groups,

TABLE I

Assignments of Infrared Bands

Compound	$\nu_{\text{Sn-X}}$	$\nu_{\text{asym (Sn-O-Sn)}}$	$\nu_{\text{asym (SnC)}}$	$\nu_{\text{sym (SnC)}}$	$\nu_{\text{asym (COO)}}$
Pr_3SnCl	330		593	507	
Bu_3SnCl	323		597	509	
Ph_3SnCl	330				
Bu_3SnF	328		612	510	
Ph_3SnF	368				
Bu_3SnBr	230		596	505	
Bu_3SnI	-		593	503	
$(\text{Pr}_3\text{Sn})_2\text{O}$		773	586	506	
$(\text{Bu}_3\text{Sn})_2\text{O}$		770	591	505	
$(\text{Ph}_3\text{Sn})_2\text{O}$		772			
$(\text{Bu}_3\text{Sn})_2$			584	495	1572
Bu_3SnOAc			609	489	1536
$\text{Bu}_3\text{Sn acrylate}$			607	508	1618
$\text{Bu}_3\text{Sn methacrylate}$			595	509	

the tin atom is four coordinate with a distorted tetrahedral geometry. Due to the complexity of these triorganotin molecules, a composite set of vibrations (asymmetric and symmetric stretching frequencies) will be observed for the SnC_3 part of the molecule rather than a single Sn-C vibration. For trigonal bipyramidal molecules with D_{3h} site symmetry only the $\nu_{\text{asym}}(\text{SnC}_2)$ is infrared active. For the molecules with C_{3v} site symmetry (distorted tetrahedron) the $\nu_{\text{asym}}(\text{SnC})$ and $\nu_{\text{sym}}(\text{SnC})$ are both infrared active. Experimentally, two vibrations are observed for all of the trialkyltin compounds in the SnC_3 region. The infrared inactive $\nu_{\text{sym}}(\text{SnC})$ mode is a weak band in the infrared for the five coordinate complexes which indicates that the site symmetry of the tin compounds is lower than D_{3h} . The $\nu_{\text{asym}}(\text{SnC})$ is sensitive to changes in coordination number as is shown in Table II. Five coordinate

TABLE II.

$\nu_{\text{asym}}(\text{SnC})$ vs. Coordination Number of Tin

Compound	ν (cm^{-1})	Coordination Number
$(\text{Bu}_3\text{Sn})_2$	584	4
Bu_3SnCl	596	4
Bu_3SnBr	596	4
Bu_3SnI	593	4
$(\text{Bu}_3\text{Sn})_2\text{O}$	591	4
Pr_3SnCl	593	4
$(\text{Pr}_3\text{Sn})_2\text{O}$	586	4
Bu_3Sn methacrylate	595	4
Bu_3SnF	612	5
Bu_3SnOAc	610	5
Bu_3Sn acrylate	607	5


triorganotin compounds exhibit the $\nu_{\text{asym}}(\text{SnC})$ between 603-612 cm^{-1} ; whereas, the $\nu_{\text{asym}}(\text{SnC})$ occurs between 584-597 cm^{-1} for the four coordinate complexes. The asymmetric SnC_3 stretching frequency is observed in the organotin containing polymers (OMP's), and occurs between 587-592 cm^{-1} . This implies that the tin moiety is four coordinate in these formulations. For the conventional coatings investigated in this study, the $\nu_{\text{asym}}(\text{SnC})$ is unobservable because of vibrations which occur in this region of the spectrum from other paint components.

The Sn-O-Sn asymmetric vibration, $\nu_{\text{asym}}(\text{SnOSn})$, has been

assigned to an intense band between 770-775 cm^{-1} for molecules of the type $(\text{R}_3\text{Sn})_2\text{O}$ (see Table I). In the commercially available coating formulations which contain bis(tri-n-butyltin) oxide (TBTO) as the toxicant (i.e. Glidden-Durkee and Navy 1020A), the $\nu_{\text{asym}}(\text{SnOSn})$ is not observed, even though the concentration of toxicant is high enough to be easily observed by infrared analysis. In the Navy 1020A formulation, which also contains tri-n-butyltin fluoride (TBTF) as toxicant, the Sn-F vibration is observed. The toxicant is presumably unchanged upon addition to the coating formulation. In the two coatings which employ TBTO as the toxicant, a band is observed at 1634 cm^{-1} in the spectrum of the Glidden-Durkee formulation, and at 1648 cm^{-1} in the spectrum of the Navy 1020A formulation. These bands were not observed in either TBTO, TBTF, or the paint formulations without toxicant. The absence of $\nu_{\text{asym}}(\text{SnOSn})$ and the presence of the band around 1640 cm^{-1} implies that the toxicant (TBTO) undergoes a reaction upon mixing with one of the components of the paint. The peak around 1640 cm^{-1} can be assigned with considerable certainty to the formulation of a tributyltin carboxylate in both of these coatings.

Upon addition of TBTO to both the Navy 1020A and Glidden-Durkee formulations without toxicant, an infrared spectrum identical to the spectrum of the formulation with toxicant was observed. (see Figure 1B and 1D, and Figure 2B and 2C). No $\nu_{\text{asym}}(\text{SnOSn})$ was observed in these spectra which again indicates that TBTO has undergone a reaction. For the Navy 1020A formulation without toxicant, the addition of tributyltin acetate (TBTA) to this coating yields a material which has an identical spectrum to that in Figure 1B. When TBTF is added to the formulation without toxicant, no reaction is observed (see Figure 1C).

It has been reported that bis(triethyltin) oxide reacts with carboxylic acids and esters (12). The TBTO in Navy 1020A was found to react with butyl acetate, one of the components of the solvent, according to the following reaction:



Tributyltin acetate precipitates from the reaction mixture upon cooling.

The $\nu_{\text{asym}}(\text{COO})$ vibration in TBTA in the solid state occurs at 1572 cm^{-1} , but when dissolved in an inert solvent such as chloroform, the band is shifted to 1640 cm^{-1} . This finding is in complete agreement with our assignment of the 1640 cm^{-1} band of the TBTO reaction product to the formation of TBTA in the coating matrix.

The Glidden-Durkee coating uses methyl isobutyl ketone and xylenes as a solvent system, and TBTO does not react with either component. However, this formulation also contains rosin, a natural product which is primarily abietic acid,

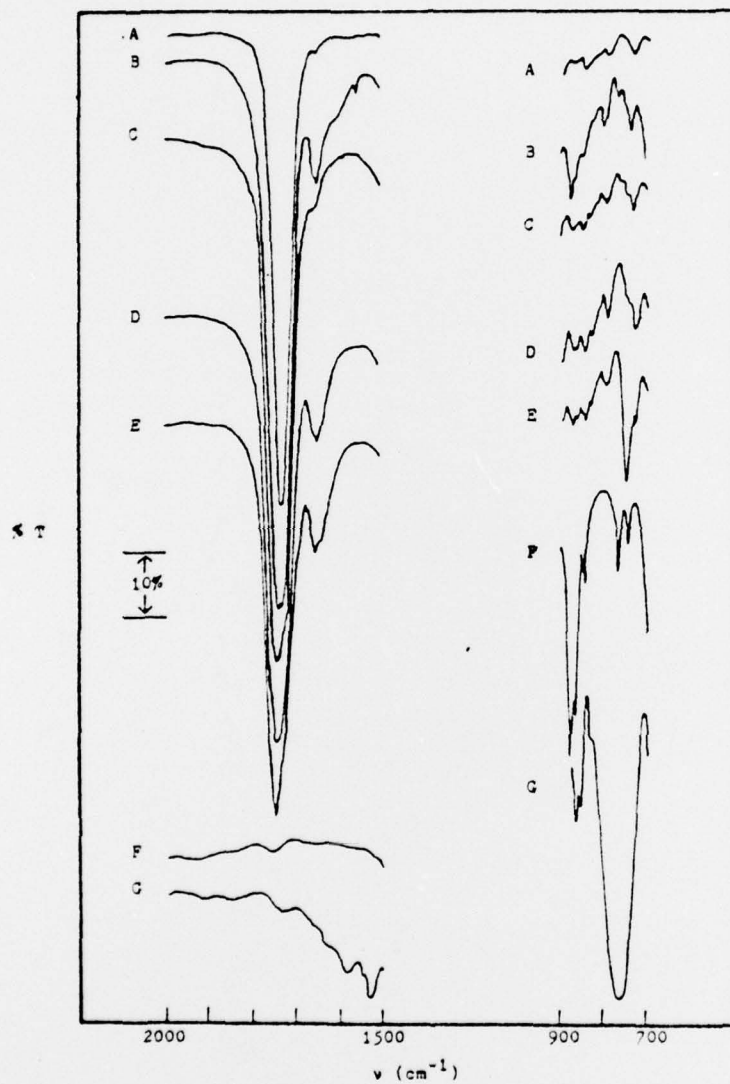


Figure 1. Infrared spectra of Navy 1020A coatings and triorganotin toxicants. (A) without toxicant, (B) with toxicant, (C) without toxicant plus added TBTF, (D) without toxicant plus added TBTO, (E) without toxicant plus added TBTA, (F) neat TBTF, (G) neat TBTO.


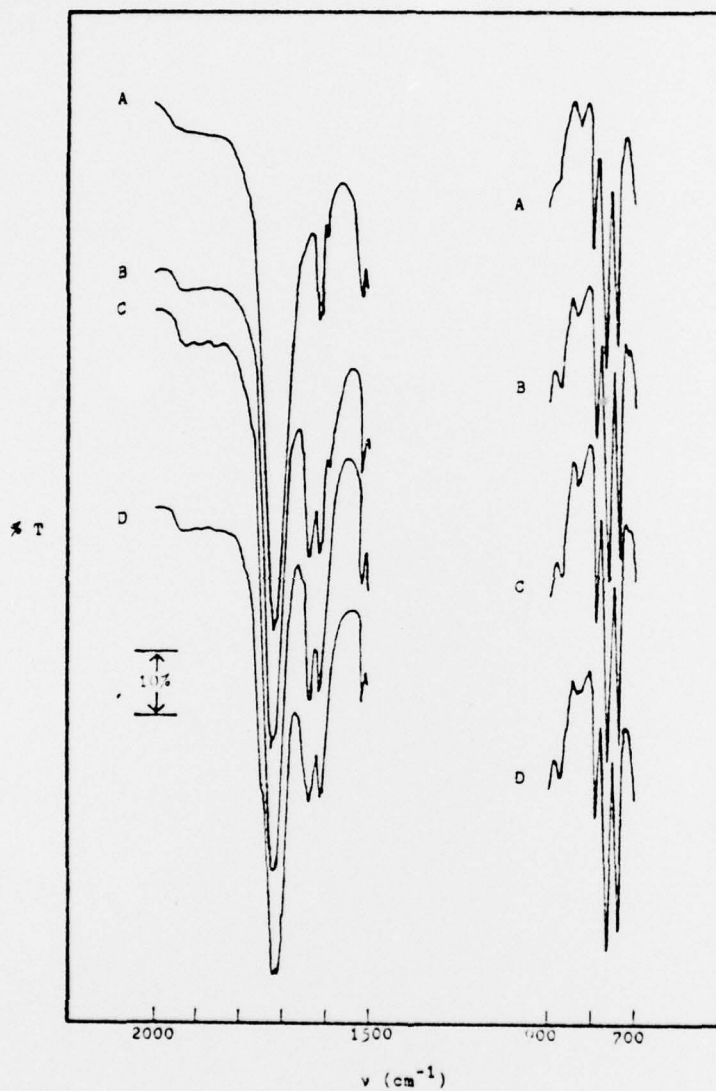


Figure 2. Infrared spectra of Glidden-Durkee coatings. (A) without toxicant, (B) with toxicant, (C) without toxicant plus added TBTA, (D) without toxicant plus added TBTO.

$C_{19}H_{29}COOH$. Bis(tributyltin) oxide does react with the rosin to yield the tributyltin ester of abietic acid, according to the following reaction (13):



The infrared spectrum of the reaction mixture exhibits a band at 1637 cm^{-1} in the spectrum of the Glidden-Durkee coating with toxicant. The products of the above reaction were not isolated.

The Alum-A-Tox coating system contains TBTF as the toxicant. It appears that no reaction occurs between the toxicant and the paint formulation, but a conclusive investigation by infrared is not possible due to bands of the paint formulation which overlap the vibrations of interest. Tributyltin fluoride did not react with the Navy 1020A so it appears likely that it will not react with the Alum-A-Tox.

The information obtained and conclusions reached on the reactions of the toxicants in the antifoulant formulations is in agreement with the observations obtained by Mossbauer spectroscopy, which are presented in the following paper.

IV. CONCLUSIONS

From this investigation, it is apparent that the toxicant in the coating must be identified in order to accurately predict the lifetime, effectiveness and environmental impact of antifouling coatings. Bis(tributyltin) oxide which was added as the toxicant in two of the conventional formulations, was found to react with one component of the paint formulation to yield a tributyltin carboxylate. Infrared and nuclear magnetic resonance spectroscopies were found to be excellent tools for the identification of the organotin species and for the investigation of molecular rearrangements.

Future work will be directed to the identification of changes in the toxicant during and after exposure of the coating to aqueous and saline environments. Efforts will also be expended to determine the chemical form of the organotin species leached from the coatings into the environment.

V. ACKNOWLEDGEMENTS

This work is a result of research sponsored by the Office of Naval Research and the NOAA Office of Sea Grant, Department of Commerce, under Grant #R/MTR-1. We also acknowledge the generous gift of the CMP's by Dr. E. Fischer of the D. Taylor Naval Ship Research and Development Center. One of us (L.M.F.) wishes to thank Charles A. Frenzel of Coastal Science Associates for his helpful discussions.

VI. REFERENCES

1. Starbird, E. A., and Sisson, R. F., National Geographic November, 623 (1973).
2. Starbird, E. A., The Readers Digest March, 123 (1974).
3. Murray, C., Chemical and Engineering News January 6, 18 (1975).
4. Vizgirda, R. J., Paint and Varnish Prod. 62, No. 12, 25 (1972).
5. Evans, C. J., J. Paint Tech. 34, Aug., 17 (1970).
6. Cremer, J. E., Biochem. J. 67, 87 (1957).
7. Sheldon, A. W., J. Paint Tech. 47, Jan., 54 (1975).
8. Smith, P., and Smith, L., Chem. in Britain 11, 208 (1975).
9. Evans, C. J., and Smith, P. J., J. Oil Col. Chem. Assoc. 58, 160 (1975).
10. Mendelsohn, J., Marchand, A., and Valade, J., J. Organomet. Chem. 6, 25 (1966).
11. Geissler, H., and Kriegsmann, H., J. Organomet. Chem. 11, 85 (1968).
12. Anderson, H. H., J. Org. Chem. 19, 1766 (1954).
13. Anderson, H. H., J. Org. Chem. 22, 147 (1957).

TECHNICAL REPORT DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Office of Naval Research Arlington, Virginia 22217 Attn: Code 472	2	Defense Documentation Center Building 5, Cameron Station Alexandria, Virginia 22314	12
Office of Naval Research Arlington, Virginia 22217 Attn: Code 1021P	6	U.S. Army Research Office P.O. Box 12211 Research Triangle Park, North Carolina 27709 Attn: CRD-AA-IP	1
ONR Branch Office 536 S. Clark Street Chicago, Illinois 60605 Attn: Dr. George Sandoz	1	Commander Naval Undersea Research and Development Center San Diego, California 92132 Attn: Technical Library, Code 133	1
ONR Branch Office 715 Broadway New York, New York 10003 Attn: Scientific Dept.	1	Naval Weapons Center China Lake, California 93555 Attn: Head, Chemistry Division	1
ONR Branch Office 1030 East Green Street Pasadena, California 91106 Attn: Dr. R. J. Marcus	1	Naval Civil Engineering Laboratory Port Hueneme, California 93041 Attn: Mr. W. S. Haynes	1
ONR Branch Office 760 Market Street, Rm. 447 San Francisco, California 94102 Attn: Dr. P. A. Miller	1	Professor O. Heinz Department of Physics and Chemistry Naval Postgraduate School Monterey, California 93940	1
ONR Branch Office 495 Summer Street Boston, Massachusetts 02210 Attn: Dr. L. H. Peebles	1	Dr. A. L. Slafkosky Scientific Advisor Commandant of the Marine Corps (Code RD-1) Washington, D.C. 20380	1
Director, Naval Research Laboratory Washington, D.C. 20390 Attn: Library, Code 2029 (ONRL) Technical Info. Div. Code 6100, 6170	6 1 1	Navy Ship Engineering Center Attn: Code 6101C (E. Morganstern) National Center, Building 2 Room 5N06 Washington, D.C. 20362	2
The Asst. Secretary of the Navy (R and D) Department of the Navy Room 4E736, Pentagon Washington, D.C. 20350	1		
Commander, Naval Air Systems Command Department of the Navy Washington, D.C. 20360 Attn: Code 310C (H. Rosenwasser)	1		

TECHNICAL REPORT DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Dr. T. C. Williams Union Carbide Corp. Chemicals and Plastics Tarrytown Technical Center Tarrytown, New York	1	Dr. M. Good Department of Chemistry University of New Orleans Lakefront New Orleans, Louisiana 70122	1
Dr. K. A. Reynard Horizons Inc. 23800 Mercantile Road Cleveland, Ohio 44122	1	Douglas Aircraft Co. 3855 Lakewood Boulevard Long Beach, California 90846 Attn: Technical Library C1 290/36-84 AUTO-Sutton	1
Dr. R. Soulen, Director Contract Research Department Pennwalt Corp. 900 First Avenue King of Prussia, Pennsylvania 19406	1	NASA-Lewis Research Center 21000 Brookpark Road Cleveland, Ohio 44135 Attn: Dr. T.T. Serafini, MS 49-1	1
Dr. A. G. MacDiarmid University of Pennsylvania Department of Chemistry Philadelphia, Pennsylvania 19174	1	Dr. J. Griffith Naval Research Laboratory Chemistry Section, Code 6120 Washington, D.C. 20375	1
Dr. E. Hedaya Union Carbide Corp. Corporate Research Laboratory Tarrytown Technical Center Tarrytown, New York 10591	1	Dr. G. Goodman Globe-Union Inc. 5757 North Green Bay Avenue Milwaukee, Wisconsin 53201	1
Dr. A. Rheingold SUNY Plattsburg Department of Chemistry Plattsburg, New York 12901	1	Dr. E. Fischer, Code 2853 Naval Ship Research and Development Center Annapolis Division Annapolis, Maryland 21402	1
Dr. C. Pittman University of Alabama Department of Chemistry University, Alabama 35486	1	Dr. Martin H. Kaufman, Head Materials Research Branch (Code 4542) Naval Weapons Center China Lake, California 93555	1
Dr. H. Allcock Pennsylvania State University University Park, Pennsylvania 16802	1		
Dr. M. Kenney Case-Western University Department of Chemistry Cleveland, Ohio 44106	1		
Dr. R. Lenz Department of Chemistry University of Massachusetts Amherst, Massachusetts 01002	1		

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER Technical Report No. 1	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) INFRARED AND NUCLEAR MAGNETIC RESONANCE ANALYSIS OF ORGANOTIN TOXICANTS FOR MARINE ANTIFOULING COATINGS		5. TYPE OF REPORT & PERIOD COVERED Interim
		6. PERFORMING ORG. REPORT NUMBER
7. AUTHOR(s) James E. Hoffman, Keith C. Kappel, Lydia M. Frenzel and Mary L. Good		8. CONTRACT OR GRANT NUMBER(s) N00014-76-C-0836
9. PERFORMING ORGANIZATION NAME AND ADDRESS Department of Chemistry University of New Orleans Lakefront, New Orleans, La. 70122		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS NR 356-626
11. CONTROLLING OFFICE NAME AND ADDRESS ONR Branch Office 536 South Clark Street Chicago, Illinois 60605		12. REPORT DATE June 24, 1977
		13. NUMBER OF PAGES Eleven (11)
14. MONITORING AGENCY NAME & ADDRESS (If different from Controlling Office) Chemistry Program Material Sciences Division Office of Naval Research, 800 N. Quincy Arlington, Virginia 22217		15. SECURITY CLASS. (of this report) Unclassified
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) "Approved for public release; distribution unlimited."		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Organotin, marine coatings, antifouling, infrared, NMR		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) Infrared and nuclear magnetic resonance spectroscopies have been employed to elucidate the chemical and structural properties of triorganotin compounds incorporated into marine antifoulant coating formulations. It is necessary to determine the molecular species of the toxicant in order to be able to predict the mechanism of toxicant release and to design new, more effective coatings. In two conventional vinyl antifoulant coatings, the toxicant was found to react with one component in the coating formulation to yield		

DD FORM 1473

1 JAN 73

EDITION OF 1 NOV 65 IS OBSOLETE
S/N 0102-014-6601

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

different triorganotin compounds. A change in the $\gamma_{\text{asym}}(\text{SnC})$ vibration was found to correlate with a change in the coordination geometry of tin. These results indicate that infrared spectroscopy is a powerful technique that can provide insights into the chemical processes occurring in the antifouling coatings.